

Table of contents

Volume 367

2018

◀ Previous issue Next issue ▶

**The 5th International Conference on Advanced Materials Sciences and Technology (ICAMST 2017)
19–20 September 2017, Makassar, Indonesia**

Accepted papers received: 16 May 2018

Published online: 12 June 2018

Open all abstracts

Preface

OPEN ACCESS 011001

The 5th International Conference on Advanced Materials Sciences and Technology
(ICAMST 2017)

+ Open abstract  View article  PDF

OPEN ACCESS 011002

The List of Committee ICAMST 2017

+ Open abstract  View article  PDF

OPEN ACCESS 011003

List of Participant ICAMST 2017

+ Open abstract  View article  PDF

OPEN ACCESS 011004

Photographs

+ Open abstract  View article  PDF

OPEN ACCESS 011005

Peer review statement

+ Open abstract  View article  PDF

This site uses cookies. By continuing to use this site you agree to our use of cookies. To find out more, see

Papers [Privacy and Cookies policy.](#)



A. Zulfi, Y. A. Rezeki, D. Edikresnha, M. M. Munir and K. Khairurrijal

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012015

Fabrication and Characterization of Monodisperse Polystyrene Latex (PSL) with Various Diameters

A Sandi, A Sawitri, A Rajak, A Zulfi, D Edikresnha, M M Munir and K Khairurrijal

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012016

Deformation of Ferrogel Based on *Carboxyl Methyl Cellulose (CMC)/Polyvinyl Alcohol (PVA)* Hydrogel

Sunaryono, M. N. Kholifah, Yudyanto, A. Taufiq, N. Mufti, R. Wulandari, Munasir and M. Diantoro

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012017

Microstructure, Hardness, and Electrical Conductivity of β -TCP/Zirconia Composites Prepared from Eggshell

Hartatiek, Yudyanto, E. K. Velayati, Y. A. Hariyanto, N. Hidayat, A. Taufiq and M. Diantoro

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012018

Influence of High Sintering Temperature Variation on Crystal Structure and Morphology of $\text{Nd}_{1.2}\text{FeO}_3$ Oxide Alloy Material by Solid-State Reaction Method

E. H. Sujiono, R. A. Imran, M. Y. Dahlan, A.C. M. Said, S. Samnur and N. Ihsan

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012019

Fabrication of PANI/Ag/AgCl/ITO-PET Flexible Film and Its Crystallinity and Electrical Properties

M. Diantoro, F. Rohmiani, A. A. Mustikasari and Sunaryono

[+ Open abstract](#) [View article](#) [PDF](#)

OPEN ACCESS

012020

Swelling Behavior in Solvent Vapor Sensing based on Quartz Crystal Microbalance (QCM) Coated Polyacrylonitrile (PAN) Nanofiber

A. Rianjanu, S. N. Hidayat, T. Julian, E. A. Suyono, A. Kusumaatmaja and K. Triyana

[+ Open abstract](#) [View article](#) [PDF](#)

This site uses cookies. By continuing to use this site you agree to our use of cookies. To find out more, see our Privacy and Cookies policy.



PAPER • OPEN ACCESS


Influence of High Sintering Temperature Variation on Crystal Structure and Morphology of $\text{Nd}_{1.2}\text{FeO}_3$ Oxide Alloy Material by Solid-State Reaction Method

To cite this article: E. H. Sujiono *et al* 2018 *IOP Conf. Ser.: Mater. Sci. Eng.* **367** 012018

View the [article online](#) for updates and enhancements.

Related content

- [Influence of Annealing Time Variation on Crystal Structure and Morphology of Oxide Material \$\text{Nd}_{1.2}\text{FeO}_3\$ by Solid-State Reaction Method](#)
E. H. Sujiono, A.C. M. Said, M. Y. Dahlan et al.
- [The Effects of Calcination Temperatures on Crystal Structures and Morphologies of \$\text{Nd}_{1.2}\text{FeO}_3\$ Synthesized by Solid-State Reaction](#)
E. H. Sujiono, M. Y. Dahlan, R. A. Imran et al.
- [Effects of Molar Ratios and Sintering Times on Crystal Structures and Surface Morphology of \$\text{Nd}_{1+x}\text{FeO}_3\$ Oxide Alloy Prepared by using Solid Reaction Method](#)
E. H. Sujiono, J. Agus, S. Samnur et al.

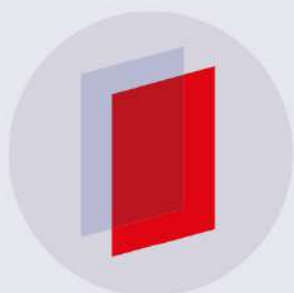

IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

Influence of High Sintering Temperature Variation on Crystal Structure and Morphology of Nd_{1.2}FeO₃ Oxide Alloy Material by Solid-State Reaction Method

E. H. Sujiono¹, R. A. Imran¹, M. Y. Dahlan¹, A.C. M. Said¹, S. Samnur¹, and N. Ihsan¹

¹Laboratory of Materials Physics, Department of Physics, *Universitas Negeri Makassar*, Makassar 90224, Indonesia.

E-mail: e.h.sujiono@unm.ac.id

Abstract. Nd_{1.2}FeO₃ powders type perovskite structure was prepared by a solid-state reaction method. This research has been conducted with the recurring heating process at high temperature. The raw material consisted of Nd₂O₃ (99.99 %) and Fe₂O₃ (99.99 %) which characterized by XRD to confirm the phase and using SEM to identify the morphology structure of the sample. Result characterized by XRD confirms the phase of NdFeO₃ and Nd₂O₃ with the formation of NdFeO₃ having the orthorhombic structure (perovskite type). The value of FWHM and the average crystal size of NdFeO₃ was obtained for each sample is 0.20° and 409 nm. While SEM studies showed the surface morphology of Nd_{1.2}FeO₃ has homogeneous granules with grain size estimates is 0.2 μm. These results indicate that sample Nd_{1.2}FeO₃ was a good candidate for gas sensor materials.

Keywords. Crystal structure, morphology, sintering, NdFeO₃ oxide alloy, and solid state method.

1. Introduction

Many researchs have been conducted on oxide compounds to be used as a gas sensor, one of them is to use a perovskite oxide that is NdFeO₃ synthesized by various methods or techniques [1–5]. NdFeO₃ known to have type orthorhombic [1, 3–6]. The nano-perovskite oxides *ABO*₃ (*A*: La, Nd, Sm, and Gd; *B*: Fe, Co and Ni; and *O*: oxygen) have high catalytic activities and high sensitivity for gas sensor material. The NdFeO₃ is mainly using in gas sensing and catalysis application [2, 3, 6]. Research on NdFeO₃ by sol-gel citrate method obtained perovskite-type NdFeO₃ can be used as an H₂S gas sensor and catalytic CO gas sensor in exhaust gas environments [3, 6]. Various synthesizing techniques have been used for synthesis NdFeO₃ alloy oxide it such as by hydrothermal method [7], combustion [8, 9], sol-gel [10], precipitation method [11], solid-state reaction method [12] and sonication assisted precipitation [13].

The solid-state reaction is one of the oldest synthesis routes for the preparation of perovskites [12]. An advantage of this method is a cheap, simple and fast method for the synthesis perovskite. Also, the product of the reaction has high purity and good crystallinity. The properties of the perovskite materials are closely related to either the preparation or sintering conditions. In the ceramics, the sintering process is essential that effect on microstructure, grain growth, and densification [14].



In this paper, we present perovskite oxide $\text{Nd}_{1.2}\text{FeO}_3$ -based by a solid state method with varying the sintering temperature using heat treatment process. Then the crystal structure and morphology of $\text{Nd}_{1.2}\text{FeO}_3$ has been characterized by X-Ray Diffraction (XRD) and Scanning Electron Microscope (SEM).

2. Materials and methods

The powders oxide $\text{Nd}_{1.2}\text{FeO}_3$ were prepared by the solid-state reaction method. Raw materials of Nd_2O_3 (Strem Chemicals, 99.99 %) and Fe_2O_3 (Sigma-Aldrich, 99.99 %) were mixed together based on a stoichiometric calculation using a molar ratio of $x = 0.2$ [15] to get an oxide alloy $\text{Nd}_{1.2}\text{FeO}_3$. Then powders were grinded for 3 h and calcined using furnace at 700°C for 6 h. Sample powders are resulting calcination then were grinded back for 5 h to get a homogeneous mixture and sintered at 950°C for 6 h.

The synthesis process and the heating are then repeated to obtain a better sample homogeneity [16]. Then mix powders produced were grinded for 3 h and calcined at 950°C for 6 h. Then the result of the calcined sample was grinded back for 5 h to maximize reaction and to increase the homogeneity and sintered as a variation of high temperatures 1000°C , 1050°C , and 1100°C for 6 h, respectively. Finally, the samples were annealed at 450°C for 1 h. Powders oxide $\text{Nd}_{1.2}\text{FeO}_3$ were characterized by XRD type Rigaku MiniFlex II $2\theta = 10^\circ$ to 70° ($\text{Cu K}\alpha$, $\lambda = 0.154\text{ nm}$) and SEM-EDS type Tescan Vega3SB to analyzed the phase composition and to confirm morphology and elemental structure.

3. Results and discussion

X-ray diffraction (XRD) pattern of samples $\text{Nd}_{1.2}\text{FeO}_3$ at high temperatures 1000°C , 1050°C , and 1100°C shown in Figure 1, respectively. According to the result of synthesis NdFeO_3 powder obtained diffraction peaks form a single phase with a perovskite structure [4, 17]. In Figure 1 shows the formation phase of NdFeO_3 and Nd_2O_3 . Formation of phase Nd_2O_3 produces another peak that regarded as an impurity phase and can reduce the sensitivity of the material as a gas sensor. Phases analysis using *Match!* software shows that dominant phase of NdFeO_3 is having the orthorhombic structure (perovskite type) with Pnma space group [18].

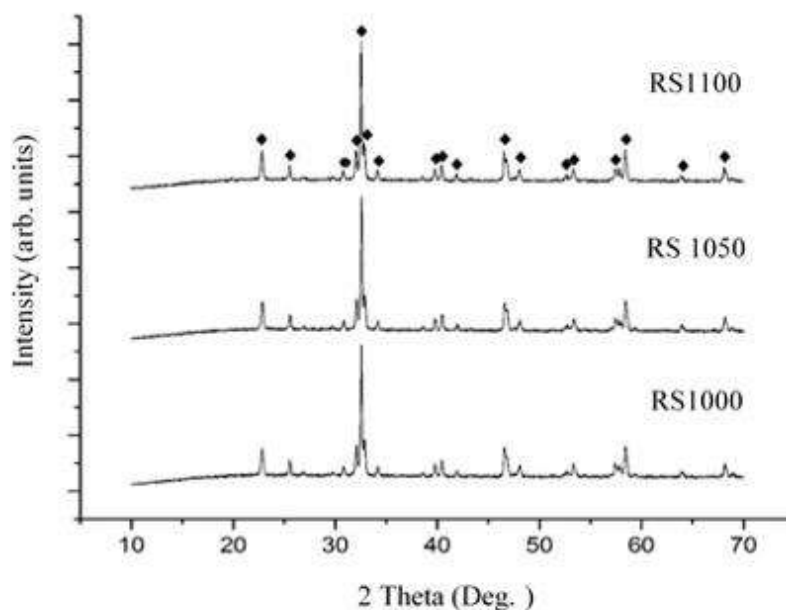


Figure 1. XRD patterns of $\text{Nd}_{1.2}\text{FeO}_3$ as variation of different temperatures (◆= NdFeO_3 , ●= Nd_2O_3).

Table 1. Data of positions (2θ), intensities and FWHM values of $\text{Nd}_{1.2}\text{FeO}_3$ phases

Sample	Identification phase	2θ ($^\circ$)	Intensity (Counts)	FWHM ($^\circ$)
RS1000	NdFeO_3	32.54	13053.33	0.20 ± 0.02
RS1050	NdFeO_3	32.56	13260.00	0.20 ± 0.02
RS1100	NdFeO_3	32.52	13810.00	0.20 ± 0.02

It can be seen from Table 1, FWHM values of NdFeO_3 phase same for all three samples at the dominant peak is hkl (121) with the peak position $2\theta = 32.5^\circ$. Synthesis of NdFeO_3 has also been done by Jada Shanker *et al.* with temperature 900°C [5], and Yabin Wang *et al.* with temperature 1000°C [4] which get similar results that phase NdFeO_3 exist at $2\theta = 32.56^\circ$ with hkl (121). FWHM value stated of homogeneity between atoms in a crystal which the smaller the FWHM value means the lattice more homogeneous or has good crystallinity, which means that the level of material quality is also getting better [4]. The crystal size can be calculated using *Debye-Scherrer* equation (1):

$$D = \frac{0.9\lambda}{\beta \cos \theta} \quad (1)$$

where λ is the wavelength of X-ray (0.15405 nm for $\text{Cu K}\alpha$), β is FWHM value at hkl (121), and θ is diffraction angle. Based on the calculation, the value of the crystal size of $\text{Nd}_{1.2}\text{FeO}_3$ which synthesized was 409.37 nm , 409.39 nm and 409.35 nm , respectively.

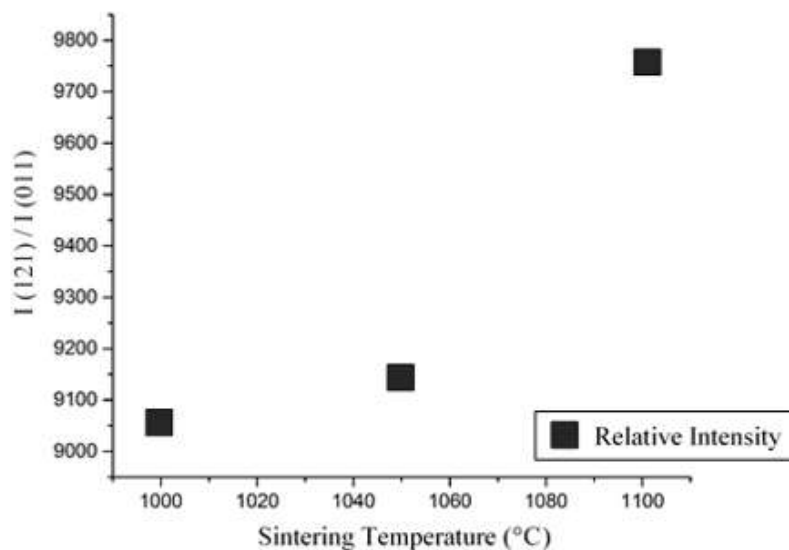


Figure 2. Relative intensity $I(121)/I(011)$ of $\text{Nd}_{1.2}\text{FeO}_3$ powders oxide material as a function of sintering temperatures.

Figure 2 shows diffraction intensity curve between the dominant of peak intensity (121) with a peak intensity of (011) for each variation of sintering temperature. In this study, we found that a significant change of peak intensity of (011) as a comparison of (121) which is indicating that the intensity of Nd_2O_3 phase decreases as the temperature of sintering increases.

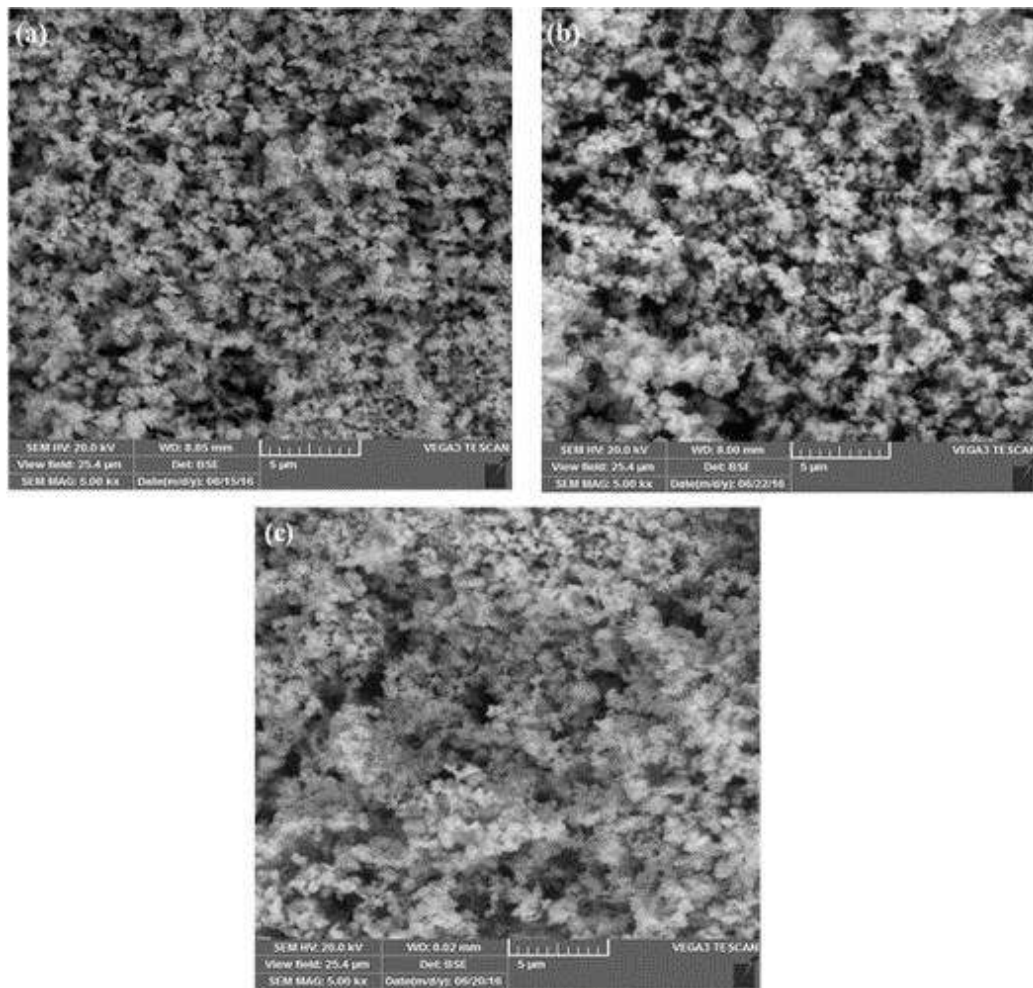


Figure 3. SEM images of sample $\text{Nd}_{1.2}\text{FeO}_3$ as a variation of sintering temperature a) RS1000, b) RS1050, and c) RS1100, respectively.

Table 2. Data composition element of $\text{Nd}_{1.2}\text{FeO}_3$ samples using EDS

Compound Norm.	Norm. C [wt%]			Error (3 Sigma) [wt%]		
	RS1000	RS1050	RS1100	RS1000	RS1050	RS1100
Oxygen	16.94	16.50	16.41	5.91	5.83	6.90
Sodium	1.32	-	-	0.38	-	-
Magnesium	0.27	-	-	0.15	-	-
Aluminium	0.25	-	-	0.14	-	-
Potassium	0.04	-	-	0.09	-	-
Titanium	0.11	-	-	0.10	-	-
Iron	21.11	21.60	19.87	1.63	1.70	1.77
Copper	0.85	0.81	0.38	1.22	0.22	0.19
Neodymium	58.99	60.94	63.15	4.26	4.52	5.23
Silicon	0.12	0.15	0.18	0.11	0.11	0.13

The morphology, crystal structure and particle size of the sample were investigated by SEM. Microstructures of polycrystalline $\text{Nd}_{1.2}\text{FeO}_3$ sintered at various temperatures are shown in Figure 3. SEM results of all samples in Figure 3, it is generally assumed that the powders $\text{Nd}_{1.2}\text{FeO}_3$ oxide alloy material have a high homogeneity level with formation small uniform granules which an estimated grain size about of $0.2 \mu\text{m}$ and the color is almost evenly gray. This powder has a very high porosity,

and this is an advantage for improving the gas-sensing characters, as has reported by Niu Xinshu *et al.* [2] and Ho *et al.* [3].

Table 2 shows the elemental composition of samples Nd_{1.2}FeO₃, were RS1000 contain Nd (58.99 wt%) and Fe (21.11 wt%), RS1050 contain Nd (60.94 wt%) and Fe (21.60 wt%), and RS1100 contain Nd (63.15 wt%) and Fe (19.87 wt%), which also contain a minor phase as shown in Table 2. That minor phase as indication due to the sample holder preparation process and no significant effect on the constituent elements of each sample.

4. Conclusions

The perovskite oxide Nd_{1.2}FeO₃ powders have been prepared by a solid-state method with the recurring heating process at high temperatures of 1000 °C, 1050 °C, and 1100 °C, respectively. The result of X-Ray diffraction analysis showed the phase of NdFeO₃ and Nd₂O₃ which phase NdFeO₃ is an orthorhombic structure with Pnma space group. The results indicate that Nd_{1.2}FeO₃ analyzed at high-temperature variation given a relatively stable quality, it can be seen the same FWHM value is 0.20° with an estimated crystalline size about of 409 nm. While SEM studies showed, the surface morphology of Nd_{1.2}FeO₃ has homogeneous granules and high porosity with an estimated grain size of 0.2 μm. The results indicate that Nd_{1.2}FeO₃ is a good candidate for gas sensor materials as has reported elsewhere.

Acknowledgments

This research was funded by Directorate Research and Community Services, Directorate General of Research and Development, Ministry of Research, Technology, and Higher Education, Republic of Indonesia, under research scheme of *Hibah Kompetensi* fiscal year 2017.

References

- [1] Khorasani-Motlagh M, Noroozifar M, Yousefi M, and Jahani S 2013 Chemical synthesis and characterization of perovskite NdFeO₃ nanocrystals via a co-precipitation method *International Journal of Nanoscience and Nanotechnology* **9** pp.7–14.
- [2] Niu X, Li H, and Liu G 2005. Preparation, characterization and photocatalytic properties of REFeO₃ (RE= Sm, Eu, Gd) *Journal of Molecular Catalysis A: Chemical* **232** pp.89–93
- [3] Ho T G *et al* 2011 *Advanced in Natural Science: Nanoscience and Nanotechnology* **2** pp 015012–15021
- [4] Wang Y S 2010 Growth rate dependence of the NdFeO₃ single crystal grown by float-zone technique *Journal Crystal Growth* **318** pp 927–931
- [5] Shanker J, Suresh M B and Babu D S 2015 *International Journal of Scientific Engineering and Research* **3** pp 194–197
- [6] Ru Z *et al* 2010 Electrical and CO-sensing properties of NdFe_{1-x}Co_xO₃ perovskite system *Journal of Rare Earths* **28** pp 591–595
- [7] Zheng W *et al* 2010 Hydrothermal synthesis of LaFeO₃ under carbonate-containing medium *Material Letters* **43** pp 19–22
- [8] Manoharan S S and Patil K C 1993 Combustion route to fine particle perovskite oxides *Journal Solid State Chemical* **102** pp 267–267
- [9] Chakraborty A, Dévi P S and Maiti H S 1995 Low temperature synthesis and some physical properties of barium-substituted lanthanum manganite (La_{1-x}Ba_xMnO₃) *Journal Materials Research* **10** pp 918–925
- [10] Cui H, Zayat M, and Levy D 2006 Epoxide assisted sol-gel synthesis of perovskite-type LaM_xFe_{1-x}O₃ (M= Ni, Co) nanoparticles *Journal of Non-Crystalline Solids* **352** pp 3035–3040
- [11] Pandya H N, Kulkarni R G, and Parsania P H 1990 Study of cerium orthoferrite prepared by wet chemical method *Materials Research. Bulletin* **25** pp 1073–1077
- [12] Yuan S *et al* 2011 Decisive role of oxygen vacancy in ferroelectric versus ferromagnetic Mn-doped BaTiO₃ thin films *Journal of Applied Physics* **109**

- [13] Singh S, Yadav B C, and Dwivedi P K 2013 Fabrication of nanobeads structured perovskite type neodymium iron oxide film: Its structural, optical, electrical and LPG sensing investigations *Sensor Actuators B: Chemical* **177** pp 730-739
- [14] Athayde D D *et al* 2016 Review of perovskite ceramic synthesis and membrane preparation methods *Ceramics International* **42** 6555–6571
- [15] Zharvan V *et al* 2017 The Effect of Molar Ratio on Crystal Structure and Morphology of $\text{Nd}_{1+x}\text{FeO}_3$ (X=0.1, 0.2, and 0.3) Oxide Alloy Material Synthesized by Solid State Reaction Method *IOP Conf. Series: Materials Science and Engineering* **202** p 1
- [16] Mir S A, Ikram M, Asokan K 2014 *Optik - International Journal for Light and Electron Optics* **125** pp 6903-6908
- [17] Shanker J, Suresh M, and Babu D 2016 Synthesis, Characterization and Electrical Properties of NdXO_3 (X=Cr, Fe) Nanoparticles *Materials Today: Proceedings* **3** pp 2091–2100
- [18] Chanda S *et al* 2013 Raman spectroscopy and dielectric properties of nanoceramic NdFeO_3 *Materials Research Bulletin* **48** pp 1688–1693